

# Fluid Model of Crystal Plasticity: Numerical Simulations of 2-turn Equal Channel Angular Extrusion

Piotr Minakowski

Preprint no. 2013 - 041



**INNOVATIVE ECONOMY**  
NATIONAL COHESION STRATEGY



**EUROPEAN UNION**  
EUROPEAN REGIONAL  
DEVELOPMENT FUND



Ph.D. Programme: Mathematical Methods in Natural Sciences (MMNS)  
e-mail: [mmns@mimuw.edu.pl](mailto:mmns@mimuw.edu.pl)  
<http://mmns.mimuw.edu.pl>

# Fluid Model of Crystal Plasticity: Numerical Simulations of 2-turn Equal Channel Angular Extrusion

Piotr Minakowski

November 27, 2013

## Abstract

Considering severe plastic deformation experiments as a motivation, the plastic behaviour of crystalline solids is treated as a flow of a highly viscous, compressible material. Starting from classical single crystal hypothesis we present a purely Eulerian set of equations describing flow of a plastic material. Moreover, we provide a thermodynamic justification of evolution of the Cauchy stress based on the Gibbs potential. Numerical simulations for a 2-turn equal channel angular extrusion are reported.

## Introduction

Recent experimental studies show that severe plastic deformations of certain materials can achieve exceptionally high strength accompanied by relatively good ductility. It is shown that simple shear is a good deformation method for structure and texture formation in metal-working. Several metal forming processes achieving severe plastic deformations are now available. We chose the equal channel angular extrusion (ECAE) because it has proven highly suitable for experimental and theoretical studies since it was first developed by Segal (Segal et al., 1981; Segal, 1995, 1999). A work piece is extruded several times through a die in the shape of curved channel with a  $90^\circ$ -angle turn. Each pass introduces additional strain. The main advantages of using ECAE in comparison to alternative experiments (e.g. rolling, forging) are minor changes in the cross-section of the billet and that one can look at various amounts of strain in a specimen.

In the presented approach the plastic behaviour of crystalline solids is treated as a highly viscous material flow through an adjustable crystal lattice (Kratohvil et al., 2009). Looking at severe plastic deformation experiments, it seems that crystalline materials at yield behave as a special kind of anisotropic, compressible, highly viscous fluid.

In early references, such as Hill and Rice (1972); Peirce et al. (1982, 1983); Asaro and Needleman (1985), the authors postulate that the Jaumann rate of

the Kirchhoff stress is related to the elastic rate of stretching by usual elastic moduli tensor. In this approach, the constitutive equation is stated phenomenologically. Moreover, it can not be derived from a Helmholtz potential. To the author's knowledge the only description of this phenomena, which is thermodynamically admissible, uses the Helmholtz potential and does not lead to a rate type model, see Srinivasa and Srinivasan (2009).

Following the paper by Rajagopal and Srinivasa (2011), we employ the Gibbs potential to derive an equation, which describes the evolution of the Cauchy stress. For detailed discussion on models of a rate type,

$$f(\dot{\mathbf{T}}, \mathbf{T}, \mathbf{L}) = 0, \quad (1)$$

where the constitutive relation consists of the stress  $\mathbf{T}$ , the rate of stress  $\dot{\mathbf{T}}$ , and the velocity gradient  $\mathbf{L}$ , we refer to Rajagopal and Srinivasa (2000, 2011).

The paper is structured as follows. In Section 1 we introduce all necessary assumptions and derive the Eulerian model of crystal plasticity, including compressible elastic stretches. Section 2 consists of the formulation of an initial boundary value problem, the description of the finite element approach, and the results of numerical simulations.

## 1 Crystal Plasticity Model

### 1.1 Kinematics

Let  $\Omega$  denote the reference configuration of the body and let  $\Omega_t$  denote the current configuration at time  $t$ . The point, which was at the position  $X \in \Omega$  in the reference configuration, is in the current configuration at time  $t$  in the position

$$x = \chi(X, t) \text{ for } X \in \Omega, x \in \Omega_t. \quad (2)$$

The mapping  $\chi(X, t)$  is continuously differentiable with respect to the position. The deformation gradient  $\mathbf{F}$  is defined through  $\frac{\partial \chi(X, t)}{\partial X}$  and we assume its multiplicative decomposition, see Kröner (1961),

$$\mathbf{F} = \frac{\partial \chi(X, t)}{\partial X} = \mathbf{F}_e \mathbf{F}_p, \quad (3)$$

where  $\mathbf{F}_e$  stands for the elastic distortion (stretches and rotations of the lattice) and  $\mathbf{F}_p$  for the plastic distortion (the distortion of the lattice due to the motion of dislocations). Moreover, the deformation gradient is non-singular and all the volumetric changes are assumed to result from the elastic stretches in the lattice,

$$\det \mathbf{F} > 0, \quad \det \mathbf{F}_p = 1, \quad \det \mathbf{F} = \det \mathbf{F}_e. \quad (4)$$

Since the velocity field is defined as  $\mathbf{v}(X, t) = \frac{\partial \chi(X, t)}{\partial t}$ , equation (3) leads to the additive decomposition of the velocity gradient

$$\nabla \mathbf{v} = \dot{\mathbf{F}} \mathbf{F}^{-1} = \dot{\mathbf{F}}_e (\mathbf{F}_e)^{-1} + \mathbf{F}_e (\dot{\mathbf{F}}_p (\mathbf{F}_p)^{-1}) (\mathbf{F}_e)^{-1} = \mathbf{L}_e + \mathbf{F}_e \mathbf{L}_p (\mathbf{F}_e)^{-1}, \quad (5)$$

where the superposed dot denotes material time derivative ( $\dot{a} = \frac{\partial a}{\partial t} + \mathbf{v} \nabla a$ ).

The evolution of the state of the body is subject to the balance of mass, momentum, angular momentum, and total energy per unit mass, which in the Eulerian coordinates take the form

$$\dot{\rho} + \rho \operatorname{div} \mathbf{v} = 0, \quad (6)$$

$$\rho \dot{\mathbf{v}} - \operatorname{div} \mathbf{T} = \mathbf{f}, \quad \mathbf{T} = \mathbf{T}^T, \quad (7)$$

$$\rho \dot{\varepsilon} = \rho r - \operatorname{div} \mathbf{q} + \mathbf{T} : \mathbf{D}, \quad (8)$$

where  $\rho(x, t)$  stands for the density,  $\mathbf{T}(x, t)$  is the Cauchy stress tensor,  $\mathbf{D}$  is the symmetric part of the velocity gradient,  $\mathbf{f}$  is the external force,  $r$  is the heat source per unit mass,  $\varepsilon$  is the specific internal energy and  $\mathbf{q}$  is the heat flux vector.

## 1.2 Evolution of the Cauchy Stress

We aim to give thermodynamic justification for the constitutive equation for the rate of stress (1). The starting point of any thermodynamical analysis is the introduction of convenient state variables. We introduce the thermodynamic variables, which depend on the temperature  $\theta$  and the Kirchhoff stress  $\mathbf{S}$

$$\begin{aligned} \varepsilon(\mathbf{S}, \theta) &- \text{specific internal energy,} \\ \Psi(\mathbf{S}, \theta) &- \text{specific Helmholtz potential,} \\ \eta(\mathbf{S}, \theta) &- \text{specific entropy.} \end{aligned}$$

The Kirchhoff stress  $\mathbf{S}$  is related to the Cauchy stress  $\mathbf{T}$  by  $\mathbf{S} = \mathbf{T}/\rho$  or  $\mathbf{S} = \mathbf{T} \det \mathbf{F} / \rho_0$ . Remembering that the determinant of the deformation gradient is the Jacobian of the mapping  $\chi$  ( $\rho(x, 0) dX = \rho(x, t) \det \mathbf{F} dx$ ), it represents the ratio of the current volume to the reference volume.

Usually the stress is defined as the derivative of a Helmholtz potential with respect to a proper strain measure. In our case we would like to avoid dependency on the strain. To this aim we transform the Helmholtz potential into the Gibbs potential  $G(\mathbf{S}, \theta)$ . The relation is given by the Legendre transformation

$$\Psi(\mathbf{S}, \theta) = G(\mathbf{S}, \theta) - \frac{\partial G(\mathbf{S}, \theta)}{\partial \mathbf{S}} : \mathbf{S}. \quad (9)$$

Knowing that the entropy is given by  $\eta(\mathbf{S}, \theta) = -\frac{\partial G(\mathbf{S}, \theta)}{\partial \theta}$  and that thermo-

dynamic variables are related by  $\varepsilon = \Psi + \theta\eta$  we substitute (9) into (8),

$$\begin{aligned} \varrho \left( \overline{G - \frac{\partial G}{\partial \mathbf{S}} : \mathbf{S} - \frac{\partial G}{\partial \theta} \theta} \right) &= \varrho r - \operatorname{div} \mathbf{q} + \mathbf{T} : \mathbf{D} \\ -\varrho \theta \frac{\dot{\overline{\partial G}}}{\partial \theta} + \varrho \left( \frac{\partial G}{\partial \mathbf{S}} : \dot{\mathbf{S}} - \frac{\partial G}{\partial \mathbf{S}} : \dot{\mathbf{S}} - \frac{\partial \overline{\partial G}}{\partial \mathbf{S}} : \mathbf{S} \right) &= \varrho r - \operatorname{div} \mathbf{q} + \mathbf{T} : \mathbf{D} \\ \varrho \theta \dot{\eta} - \varrho \frac{\partial^2 G}{\partial \mathbf{S}^2} \dot{\mathbf{S}} : \mathbf{S} &= \varrho r - \operatorname{div} \mathbf{q} + \mathbf{T} : \mathbf{D} \\ \varrho \theta \dot{\eta} &= \varrho r - \operatorname{div} \mathbf{q} + \varrho \left( \mathbf{S} : \left( \mathbf{D} + \frac{\partial^2 G}{\partial \mathbf{S}^2} \dot{\mathbf{S}} \right) \right). \end{aligned}$$

The second law of thermodynamics involving the specific entropy (Clausius–Duhem inequality), takes the form

$$\varrho \dot{\eta} + \operatorname{div} \left( \frac{\mathbf{q}}{\theta} \right) - \frac{\varrho r}{\theta} \geq 0. \quad (10)$$

We identify the rate of dissipation (the rate of entropy production per unit mass) as

$$\xi = \mathbf{S} : \left( \mathbf{D} + \frac{\partial^2 G}{\partial \mathbf{S}^2} \dot{\mathbf{S}} \right) = \mathbf{S} : \left( \mathbf{D} - \mathcal{A} \dot{\mathbf{S}} \right), \quad (11)$$

where  $\mathcal{A} = -\frac{\partial^2 G}{\partial \mathbf{S}^2}$  stands for the fourth order symmetric elastic compliance tensor.

In order to obtain the objective stress-strain constitutive relation (1) we follow Rajagopal and Srinivasa (2011). The right hand side of (11) consists of  $\mathbf{D}$  and  $\mathcal{A}$ , both objective tensors, and  $\dot{\mathbf{S}}$ , which itself is not objective (however  $\mathbf{S} : \mathcal{A} \dot{\mathbf{S}}$  is objective). To overcome this difficulty we notice that, due to the fact that  $G$  is an isotropic function of  $\mathbf{S}$ ,  $\mathcal{A} \dot{\mathbf{S}}$  can be expressed by  $\mathcal{A} \dot{\mathbf{S}} = \alpha_1 \mathbf{I} + \alpha_2 \mathbf{S} + \alpha_3 \mathbf{S}^2$ , where  $\alpha_i$  ( $i = 1, 2, 3$ ) are scalar functions of the invariants of  $\mathbf{S}$ . From the representation of  $\mathcal{A} \dot{\mathbf{S}}$  we can observe that  $(\mathcal{A} \dot{\mathbf{S}}) \mathbf{S} = \mathbf{S} (\mathcal{A} \dot{\mathbf{S}})$ . Now let us consider an arbitrary tensor  $\mathbf{W}$  and the expression  $\mathbf{S} : \mathcal{A} (\mathbf{W} \mathbf{S} - \mathbf{S} \mathbf{W})$ . From the symmetry of  $\mathcal{A}$  and  $\mathbf{S}$  ( $\mathbf{S} = \mathbf{S}^T$ ) together with the above observation we obtain

$$\mathbf{S} : \mathcal{A} (\mathbf{W} \mathbf{S} - \mathbf{S} \mathbf{W}) = \mathcal{A} \dot{\mathbf{S}} : (\mathbf{W} \mathbf{S} - \mathbf{S} \mathbf{W}) = \mathbf{W} : ((\mathcal{A} \dot{\mathbf{S}}) \mathbf{S} - \mathbf{S} (\mathcal{A} \dot{\mathbf{S}})) = 0. \quad (12)$$

By adding (12) to (11) we get

$$\xi = \mathbf{S} : \left( \mathbf{D} - \mathcal{A} (\dot{\mathbf{S}} + \mathbf{W} \mathbf{S} - \mathbf{S} \mathbf{W}) \right). \quad (13)$$

Let us denote the dissipative part of  $\mathbf{D}$  by  $\mathbf{D}_p$  and the inversion of  $\mathcal{A}$  by  $\mathcal{C}$ ,

$$\mathbf{D}_p = \mathbf{D} - \mathcal{A} (\dot{\mathbf{S}} + \mathbf{W} \mathbf{S} - \mathbf{S} \mathbf{W}), \quad \dot{\mathbf{S}} + \mathbf{W} \mathbf{S} - \mathbf{S} \mathbf{W} = \mathcal{C} (\mathbf{D} - \mathbf{D}_p). \quad (14)$$

To reformulate (14) in terms of the Cauchy stress we substitute  $\mathbf{S} = \mathbf{T} / \varrho$  and deduce

$$\dot{\mathbf{T}} + \mathbf{T} \operatorname{div} \mathbf{v} + \mathbf{W} \mathbf{T} - \mathbf{T} \mathbf{W} = \varrho \mathcal{C} (\mathbf{D} - \mathbf{D}_p). \quad (15)$$

Finally we obtain the material rate of Cauchy stress. By choosing an arbitrary tensor  $\mathbf{W}$  as the skew-symmetric part of the velocity gradient  $\mathbf{W} = \frac{1}{2}(\nabla\mathbf{v} - (\nabla\mathbf{v})^T)$ , we conclude that the evolution of the Cauchy stress is described by the Jaumann rate (15).

In what follows we confine ourselves to isotropic elastic response, by specifying the fourth order elastic tensor  $\mathcal{C}$  as  $\mathcal{C}(\mathbf{D} - \mathbf{D}_p) = \lambda(\text{tr}(\mathbf{D} - \mathbf{D}_p))\mathbf{I} + 2\mu(\mathbf{D} - \mathbf{D}_p)$ , where  $\lambda$  and  $\mu$  are the Lamé coefficients,  $\mathcal{C} = \lambda\mathbf{I} \otimes \mathbf{I} + 2\mu\mathbf{I}$ ,  $\mathcal{C}_{IJKL} = \lambda\delta_{IJ}\delta_{KL} + \mu(\delta_{IK}\delta_{JL} + \delta_{JK}\delta_{IL})$ .

### 1.3 Single Crystal Hypothesis

Plastic effects are modelled as the deformations of a material due to the flow of material dislocations through the lattice. The single-crystal hypothesis is based on the assumption that the motion of dislocations in crystalline materials take place in preferred slip directions on preferred slip planes. The slip directions are described by the constant, orthonormal, unit vectors  $\mathbf{s}_0^{(i)}$  and  $\mathbf{m}_0^{(i)}$ , where  $\mathbf{s}_0^{(i)}$  is in the direction of the slip and  $\mathbf{m}_0^{(i)}$  is normal to the slip plane. These two vectors indicate slip systems ( $i = 1, 2, \dots, N$ ) and are given by crystallographic structure. The plastic part of the velocity gradient  $\mathbf{L}_p$  is assumed to be given by (Rice, 1971)

$$\mathbf{L}_p = \sum_{i=1}^N \nu^{(i)} \mathbf{s}_0^{(i)} \otimes \mathbf{m}_0^{(i)}, \quad \mathbf{D}_p = \sum_{i=1}^N \nu^{(i)} \text{sym}(\mathbf{s}_0^{(i)} \otimes \mathbf{m}_0^{(i)}), \quad (16)$$

with the slip rates  $\nu^{(i)}(x, t)$  resisting flow on the individual slip system. Moreover, we introduce the current slip directions and those normal to the current slip directions, which depend on the deformation gradient through the relation  $\mathbf{s}^{(i)} = \mathbf{F}_e \mathbf{s}_0^{(i)}$ ,  $\mathbf{m}^{(i)} = \mathbf{F}_e^{-T} \mathbf{m}_0^{(i)}$ . Finally we obtain the flow rule

$$\mathbf{L} = \mathbf{L}_e + \sum_{i=1}^N \nu^{(i)} \mathbf{F}_e \mathbf{s}_0^{(i)} \otimes \mathbf{m}_0^{(i)} (\mathbf{F}_e)^{-1} = \mathbf{L}_e + \sum_{i=1}^N \nu^{(i)} \mathbf{s}^{(i)} \otimes \mathbf{m}^{(i)}. \quad (17)$$

To complete a system of equations, the slip rates  $\nu^{(i)}$  have to be specified. Following Peirce et al. (1983), we employ the common assumption that rate-sensitivity function is the power-law function

$$\nu^{(i)} = \nu_0 \text{sgn}(\tau^{(i)}) \left( \frac{|\tau^{(i)}|}{\tau_c^{(i)}} \right)^{1/m}, \quad (18)$$

where the resolved shear stresses  $\tau^{(i)}$  represent the Cauchy stress resolved on each slip system  $\tau^{(i)} = \mathbf{s}^{(i)} \cdot \mathbf{T} \mathbf{m}^{(i)}$ ,  $1/m$  is a rate sensitivity parameter,  $\nu_0$  a reference slip rate, and  $\tau_c$  is a critical resolved shear stress. The critical stresses  $\tau_c^{(i)}$  representing dissipative internal forces that oppose the slip are assumed to be governed by the evolution equation

$$\dot{\tau}_c^{(i)} = \sum_j H_{ij} |\nu^{(j)}|, \quad (19)$$

where hardening coefficients  $H_{ij}$  are functions of accumulated slip rate and  $\tau_c|_{t=0} = \tau_0$ .

Let us notice that under the above assumptions the second law of thermodynamics is satisfied

$$\xi = \mathbf{T} : \mathbf{D}_p = \sum_{i=1}^N \nu^{(i)} \mathbf{T} : \left( \mathbf{s}^{(i)} \otimes \mathbf{m}^{(i)} \right) = \sum_{i=1}^N \nu^{(i)} \tau^{(i)} = \sum_{i=1}^N \nu_0 |\tau^{(i)}| \left( \frac{|\tau^{(i)}|}{\tau_c^{(i)}} \right)^{\frac{1}{m}} \geq 0. \quad (20)$$

#### 1.4 Evolution of the Slip Systems

Our goal is to formulate a system of equations in the current configuration independently of the deformation gradient. To this aim we employ ideas from Cazacu and Ionescu (2010b,a). By taking the time derivative of the relation  $\mathbf{s}^{(i)} = \mathbf{F}_e \mathbf{s}_0^{(i)}$  and substituting  $\dot{\mathbf{F}}_e$  from (5), we obtain the equation that describes the evolution of the slip directions

$$\dot{\mathbf{s}}^{(i)} = \left( \nabla \mathbf{v} - \sum_i \nu^{(i)} \mathbf{s}^{(i)} \otimes \mathbf{m}^{(i)} \right) \mathbf{F}_e \mathbf{s}_0^{(i)}, \quad \dot{\mathbf{s}}^{(i)} = \left( \nabla \mathbf{v} - \sum_i \nu^{(i)} \mathbf{s}^{(i)} \otimes \mathbf{m}^{(i)} \right) \mathbf{s}^{(i)}. \quad (21)$$

In Section 2 we will restrict ourselves to the plane strain case. We consider projections of three dimensional slip systems onto the plane. Due to the geometrical restrictions of in-plane model of FCC crystal, we will consider only three slip systems (for detailed discussion see Cazacu and Ionescu (2010b)). Two dimensional vectors corresponding with  $i$ -th slip system can be described by their angle of lattice rotation  $\varphi_i$  and the scalars  $s_i, m_i$  responsible for elastic stretching. Since all three slip systems are rotating together, we can characterise the rotation by specifying the angles  $\varphi_i$  for  $i \in \{1, 2, 3\}$  as  $\varphi_1 = \varphi + \phi$ ,  $\varphi_2 = \varphi$ , and  $\varphi_3 = \varphi - \phi$ , where  $\phi = 54.7^\circ$ ,

$$\mathbf{s}^{(i)} = s_i (\cos \varphi_i, \sin \varphi_i), \quad \mathbf{m}^{(i)} = m_i (-\sin \varphi_i, \cos \varphi_i). \quad (22)$$

We reformulate vectorial equations (21) in terms of the scalar unknowns  $(\varphi, s_1, m_1, s_2, m_2, s_3, m_3)$ ,

$$\dot{\varphi} = (-\sin \varphi, \cos \varphi)^T \left( \nabla \mathbf{v} - \sum_{i=1}^3 \nu^{(i)} \mathbf{s}^{(i)} \otimes \mathbf{m}^{(i)} \right) s_2 (\cos \varphi, \sin \varphi), \quad (23)$$

$$\dot{s}_i = (\cos \varphi_i, \sin \varphi_i)^T \left( \nabla \mathbf{v} - \sum_{i=1}^3 \nu^{(i)} \mathbf{s}^{(i)} \otimes \mathbf{m}^{(i)} \right) s_i (\cos \varphi_i, \sin \varphi_i); \quad i \in \{1, 2, 3\}, \quad (24)$$

$$\dot{m}_i = (-\sin \varphi_i, \cos \varphi_i)^T \left( \nabla \mathbf{v} - \sum_{i=1}^3 \nu^{(i)} \mathbf{s}^{(i)} \otimes \mathbf{m}^{(i)} \right) m_i (-\sin \varphi_i, \cos \varphi_i); \quad i \in \{1, 2, 3\}$$

## 2 2-turn Equal Channel Angular Extrusion

ECAE is based on forcing a specimen through an L-shape channel of a constant cross-section. Simple shear takes place in the thin layer at the channel turn. The process is repeated, a couple of times (typically up to 10) in order to obtain a very large (severe) plastic deformation and a fine grain structure. The first report on the use of a 2-turn channel is due to Liu et al. (1998). Later the idea was extended to multi-pass ECAE by Nakashima et al. (2000).

The Eulerian system of equations derived in Section 1 allows us to consider more than one turn in a single domain. We chose a 2-turn channel to show the main features of the presented approach. For experimental and numerical studies of a 2-turn ECAE we refer to Rosochowski and Olejnik (2002, 2008).

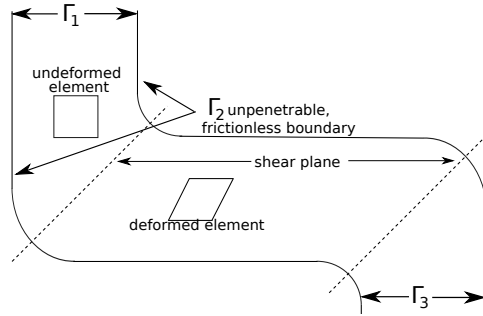


Figure 1: Scheme of 2-turn ECAE experiment

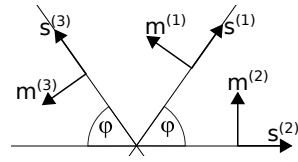


Figure 2: Scheme of slip systems

### 2.1 Initial-boundary Value Problem

Our domain  $\Omega$  is the 2-turn channel (see Figure 1). In the Eulerian description of plane-strain crystal plasticity the unknowns are: the velocity  $\mathbf{v}(x, t)$ , the Cauchy stress  $\mathbf{T}(x, t)$ , the density  $\varrho(x, t)$ , and the orientation of the lattice  $\varphi(x, t)$ . The boundary of the domain is divided into three parts: the inflow boundary  $\Gamma_1$ , the impenetrable boundary  $\Gamma_2$  and the outflow boundary  $\Gamma_3$ . The boundary conditions are set to be: the Dirichlet inflow condition on the velocity and the lattice orientation,  $\mathbf{v}|_{\Gamma_1} = \mathbf{v}_{in} = (0, -1)$ ,  $\varphi|_{\Gamma_1} = \varphi_{in} = 0$ , the perfect-slip on  $\Gamma_2$ , and the do-nothing condition on  $\Gamma_3$ . The material parameters and characteristic values are taken to be: the density  $\varrho_0 = 3000 \frac{kg}{m^3}$ , the velocity  $V = 10^{-5} \frac{m}{s} = 10 \frac{\mu m}{s}$ , the length  $L = 10^{-2} m$ , the reference slip rate  $\nu_0 = 10^{-3} \frac{1}{s}$ , the reference stress  $\tau_0 = 70 MPa$ , the Young's modulus  $E = 1000 \tau_0$ , the Poisson's ratio  $\nu_{pois} = 0.35$ , and the rate sensitivity parameter  $m = 0.05$  ( $1/m = 20$ ). The material parameters correspond to aluminium and the characteristic values reflect ECAE experiments. As initial values we put  $\mathbf{v}(x, 0) = 0$ ,  $\mathbf{T}(x, 0) = 0$ ,  $\tau_c(x, 0) = \tau_0$ ,  $\varrho(x, 0) = 1$ ,  $\varphi(x, 0) = 0$  and  $m_i(x, 0) = s_i(x, 0) = 1$ ,  $\forall i \in \{1, 2, 3\}$ .



After rescaling of the system we get the following set of equations

$$\begin{aligned}
\varrho_{,t} + \operatorname{div}(\varrho \mathbf{v}) &= 0, \\
R_1 \varrho \dot{\mathbf{v}} - \operatorname{div} \mathbf{T} &= 0, \\
\dot{\mathbf{T}} + \mathbf{T} \operatorname{div} \mathbf{v} + \mathbf{W} \mathbf{T} - \mathbf{T} \mathbf{W} &= \varrho \mathcal{C}(\mathbf{D} - \mathbf{D}_p), \\
\dot{\varphi} &= (-\sin \varphi, \cos \varphi)^T \left( \nabla \mathbf{v} - R_2 \sum_{i=1}^3 \nu^{(i)} \mathbf{s}^{(i)} \otimes \mathbf{m}^{(i)} \right) s_2(\cos \varphi, \sin \varphi),
\end{aligned} \tag{26}$$

where  $\mathbf{D}_p$ ,  $\nu^{(i)}$ ,  $m_i$ ,  $s_i$  and  $\dot{\tau}_c^{(i)}$  are given by (16), (18), (24), (25) and (19), respectively.

Two characteristic numbers appear in the system,  $R_1 = \frac{\varrho_0 V^2}{L \tau_0} \approx 10^{-12}$  and  $R_2 = \frac{L \nu_0}{V} = 1$ . The very small value of  $R_1$  justifies the restriction to quasi-static case, which is common in plasticity. However we keep the time derivative in the balance equation (7).

Moreover, we specify the hardening matrix  $H_{ij} = H = H_0 \operatorname{sech}^2\left(\frac{H_0 \nu_{acc}}{\tau_s - \tau_0}\right)$ , where the initial hardening rate  $H_0 = 8.9 \tau_0$ , the saturation strength  $\tau_s = 1.8 \tau_0$  and the accumulated slip  $\nu_{acc}(t) = \sum_i \int_0^t |\nu^{(i)}| dt$ , see Peirce et al. (1983).

## 2.2 Finite Element Formulation

Inspired by the numerical methods of fluid dynamics, finite element Eulerian representation is formulated and applied to a solution of the flow adjustment initial-boundary value problem for the 2-turn equal channel angular extrusion, see Section 2.1.

The domain  $\Omega$  is approximated by a simplicial triangulation  $\mathcal{T}_h$ . Time is discretized by a one step finite difference. The discretization in space consists of P2 elements for the velocity, P1 for the density and the lattice rotations (all continuous) and P1-discontinuous for the Cauchy stress and the slip rates. We define the finite-dimensional spaces

$$\begin{aligned}
\mathbb{V}_h &= \{v_h \in W^{1,2}(\Omega; \mathbb{R}^2); \mathbf{v}|_{\Gamma_1} = (0, -1), \mathbf{v}|_K \in \mathcal{P}_2(K)^2 \forall K \in \mathcal{T}_h\}, \\
\mathbb{R}_h &= \{\varrho_h \in W^{1,2}(\Omega; \mathbb{R}); \varrho_h|_{\Gamma_1} = 1, \varrho_h|_K \in \mathcal{P}_1(K) \forall K \in \mathcal{T}_h\}, \\
\mathbb{T}_h &= \{\mathbf{T}_h \in W^{1,2}(\Omega; \mathbb{R}_{sym}^{2 \times 2}); \mathbf{T}_h|_K \in \mathcal{P}_1(K)^{2 \times 2} \forall K \in \mathcal{T}_h\}, \\
\mathbb{N}_h &= \{\nu_h \in L^2(\mathbb{R}); \nu_h|_1 \in \mathcal{P}_1(K) \forall K \in \mathcal{T}_h\}, \\
\mathbb{A}_h &= \{\varphi_h \in W^{1,2}(\Omega; \mathbb{R}); \varphi_h|_{\Gamma_1} = 0, \varphi_h|_K \in \mathcal{P}_1(K) \forall K \in \mathcal{T}_h\}.
\end{aligned}$$

The slip rates are added to the system (26) as variables. We discretize the system (26) in a mixed finite element space and solve the following problem. Find  $(\mathbf{v}_h, \varrho_h, \mathbf{T}_h, \nu_{1h}, \nu_{2h}, \nu_{3h}, \varphi_h) \in \mathbb{V}_h \times \mathbb{R}_h \times \mathbb{T}_h \times \mathbb{N}_h \times \mathbb{N}_h \times \mathbb{N}_h \times \mathbb{A}_h$ , such

that

$$\begin{aligned}
& (\varrho_{h,t}, z_\varrho) + (\mathbf{v}_h \nabla \varrho_h, z_\varrho) + (\varrho_h \operatorname{div}(\mathbf{v}_h), z_\varrho) = 0 \quad \forall z_\varrho \in \mathbb{R}_{h0}, \\
& R_1 (\varrho_h \dot{\mathbf{v}}_h, \mathbf{z}_v) + (\mathbf{T}_h, \nabla(\mathbf{z}_v)) + (\mathbf{T}_h \mathbf{n} \cdot \mathbf{n}, \mathbf{z}_v \cdot \mathbf{n})_{\Gamma_2} + \frac{\beta}{h} (\mathbf{v}_h \cdot \mathbf{n}, \mathbf{z}_v \cdot \mathbf{n})_{\Gamma_2} = 0 \quad \forall \mathbf{z}_v \in \mathbb{V}_{h0}, \\
& \left( \dot{\mathbf{T}}_h + \mathbf{T}_h \operatorname{div} \mathbf{v}_h + \mathbf{W}_h \mathbf{T}_h - \mathbf{T}_h \mathbf{W}_h, \mathbf{Z}_T \right) - (\varrho \mathcal{C}(\mathbf{D}_h - \mathbf{D}_{p_h}), \mathbf{Z}_T) + (\mathbf{Z}_T \mathbf{n} \cdot \mathbf{n}, \mathbf{v}_h \cdot \mathbf{n})_{\Gamma_2} = 0 \quad \forall \mathbf{Z}_T \in \mathbb{T}_h, \\
& \left( \nu_h^{(i)} - \operatorname{sgn}(\mathbf{T}_h : \mathbf{s}_h^{(i)} \otimes \mathbf{m}_h^{(i)}) \left( \frac{|\mathbf{T}_h : \mathbf{s}_h^{(i)} \otimes \mathbf{m}_h^{(i)}|}{\tau_c^{(i)}} \right)^{20}, z_{\nu i} \right) = 0 \quad \forall z_{\nu i} \in \mathbb{N}_h \text{ and } i \in \{1, 2, 3\}, \\
& \left( \dot{\varphi}_h - (-\sin \varphi_h, \cos \varphi_h)^T \left( \nabla \mathbf{v}_h - R_2 \sum_{i=1}^3 \nu_h^{(i)} \mathbf{s}_h^{(i)} \otimes \mathbf{m}_h^{(i)} \right) s_{2h}(\cos \varphi_h, \sin \varphi_h), z_\varphi \right) = 0 \quad z_\varphi \in \mathbb{A}_h,
\end{aligned} \tag{27}$$

where  $(\cdot, \cdot)$  is the standard  $L_2$  inner product. The boundary conditions on the impenetrable, frictionless boundary  $\Gamma_2$  are imposed by the Nitsche's method:  $(\mathbf{Z}_T \mathbf{n} \cdot \mathbf{n}, \mathbf{v} \cdot \mathbf{n})_{\Gamma_2} + (\mathbf{T} \mathbf{n} \cdot \mathbf{n}, \mathbf{z}_v \cdot \mathbf{n})_{\Gamma_2} + \frac{\beta}{h} (\mathbf{v} \cdot \mathbf{n}, \mathbf{z}_v \cdot \mathbf{n})_{\Gamma_2}$  with  $\beta = 10$ , see Freund and Stenberg (1995).

To solve the system (27) we employ a non-linear Newton-Ralphson solver with an analytic Jacobian. Implementation is done in the software package FEniCS (Logg et al., 2012). A linear system is solved by a direct solver.

Moreover, the critical resolved shear stresses and the stretch of slip directions are updated after each time step according to (19), (24), and (25).

### 2.3 Results

We present the results of computations at the moment when a steady state is reached (see Figure 3). We treat plastic material as a fluid so it fills the entire domain, as opposed to models where empty zones (close to outer turn) are reported (Rosochowski and Olejnik, 2008). The velocity profile is typical of flow problems.

We can observe that plastic slip occurs only in the vicinity of shear planes where the channel turns. The accumulated slip has highest values close to the inner turns. Density is almost constant, although it changes in the neighbourhood of the curved part of the boundary and it is higher before the first turn than in the rest of the domain. The lattice rotation also changes nearby the shear planes in the direction of turn.

In Figure 4 we observe the behaviour of individual slip systems. The arrangement of slip directions is presented in Figure 1. We notice that the activation of a particular slip system depends on its position relative to the shear plane. The second slip system is almost not active but we need to take it into account due to compressibility.

Simulations were conducted for two different meshes: 5278 vertices (10252 cells) and 21289 vertices (41974 cells). We conclude that the problem is mesh independent. Presented results were computed on the finer mesh.

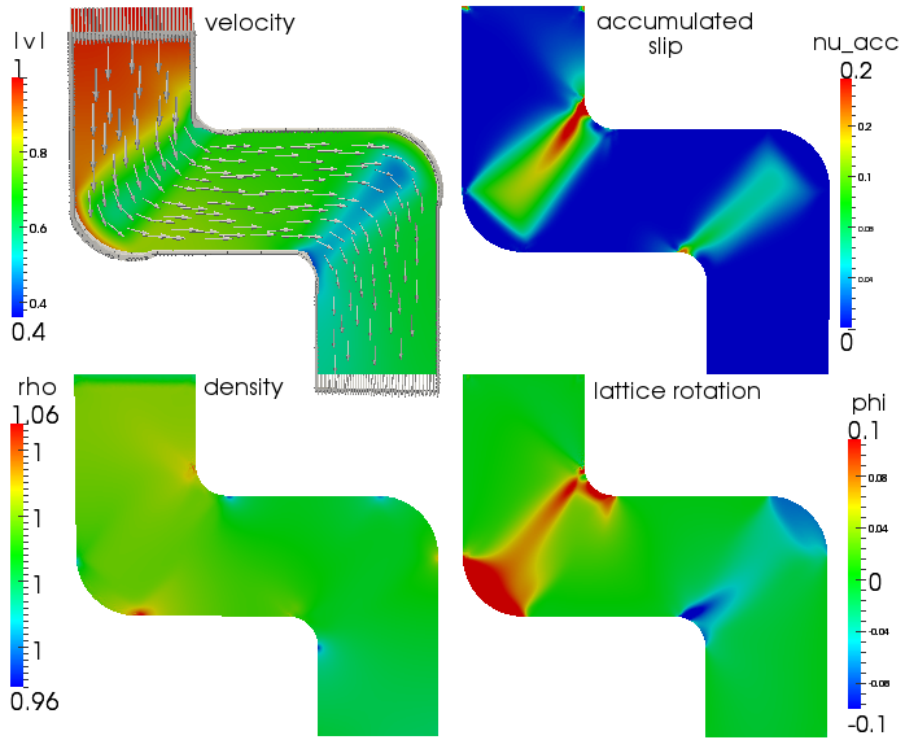


Figure 3: Computed variables: velocity magnitude (top-left), accumulated slip (top-right), density (bottom-left), lattice rotation (bottom-right).

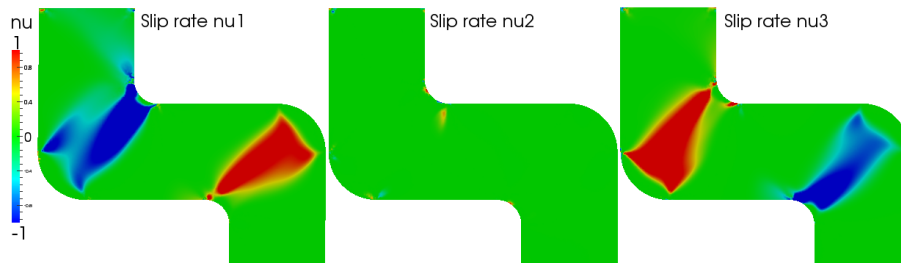


Figure 4: Behaviour of slip rates on individual slip systems in the 2-turn channel.

### 3 Conclusions

In this paper we derived a model of crystal plasticity that includes compressible linear elasticity. Stretches and rotations of the slip systems were taken into account and the evolution of the Cauchy stress was justified by thermodynamical discussion.

We formulated the finite element discretization scheme, which was used to solve the fully coupled problem. Performed numerical simulations show the capabilities of the method applied. An important elements of the model are the elastic stretches, because they allow us to reduce high values of stress in the vicinity of inner turns.

The presented approach is purely Eulerian and its main advantage is the ability to capture high strains, due to ECAE with multiple turns. In the future we plan to abandon the plane strain assumption and compute 3D models including the full set of the slip systems, even though this will require the use of parallel computing.

## Acknowledgement

This work was supported by the International Ph.D. Projects Programme of the Foundation for Polish Science operated within the Innovative Economy Operational Programme 2007-2013 funded by European Regional Development Fund (Ph.D. Programme: Mathematical Methods in Natural Sciences). Research was partially supported by the GAČR grant no. P107/12/0121 and the NCN grant no. 2012/07/N/ST1/03369.

## References

- Asaro, R.; Needleman, A.: Overview no. 42 texture development and strain hardening in rate dependent polycrystals. *Acta Metallurgica*, 33, 6, (1985), 923–953.
- Cazacu, O.; Ionescu, I. R.: Augmented lagrangian method for eulerian modeling of viscoplastic crystals. *Computer Methods in Applied Mechanics and Engineering*, 199, 912, (2010a), 689 – 699.
- Cazacu, O.; Ionescu, I. R.: Dynamic crystal plasticity: An eulerian approach. *Journal of the Mechanics and Physics of Solids*, 58, 6, (2010b), 844 – 859.
- Freund, J.; Stenberg, R.: On weakly imposed boundary conditions for second order problems. *Proceedings of the International Conference on Finite Elements in Fluids*, pages 327–336.
- Hill, R.; Rice, J.: Constitutive analysis of elastic-plastic crystals at arbitrary strain. *Journal of the Mechanics and Physics of Solids*, 20, 6, (1972), 401 – 413.
- Kratochvíl, J.; Kružík, M.; Sedláček, R.: A model of ultrafine microstructure evolution in materials deformed by high-pressure torsion. *Acta Materialia*, 57, 3, (2009), 739–748.
- Kröner, E.: On the plastic deformation of polycrystals [zur plastischen verformung des vielkristalls]. *Acta Metallurgica*, 9, 2, (1961), 155–161.

- Liu, Z.; Liang, G.; Wang, E.; Wang, Z.: The effect of cumulative large plastic strain on the structure and properties of a CuZn alloy. *Materials Science and Engineering: A*, 242, 12, (1998), 137 – 140.
- Logg, A.; Mardal, K.-A.; Wells, G. N., eds.: *Automated Solution of Differential Equations by the Finite Element Method*, vol. 84 of *Lecture Notes in Computational Science and Engineering*. Springer (2012).
- Nakashima, K.; Horita, Z.; Nemoto, M.; Langdon, T. G.: Development of a multi-pass facility for equal-channel angular pressing to high total strains. *Materials Science and Engineering: A*, 281, 12, (2000), 82 – 87.
- Peirce, D.; Asaro, R.; Needleman, A.: An analysis of nonuniform and localized deformation in ductile single crystals. *Acta Metallurgica*, 30, 6, (1982), 1087–1119.
- Peirce, D.; Asaro, R.; Needleman, A.: Material rate dependence and localized deformation in crystalline solids. *Acta Metallurgica*, 31, 12, (1983), 1951–1976.
- Rajagopal, K.; Srinivasa, A.: A thermodynamic frame work for rate type fluid models. *Journal of Non-Newtonian Fluid Mechanics*, 88, 3, (2000), 207 – 227.
- Rajagopal, K. R.; Srinivasa, A. R.: A gibbs-potential-based formulation for obtaining the response functions for a class of viscoelastic materials. *Proc. R. Soc. A*, 467, 2125, (2011), 39–58.
- Rice, J.: Inelastic constitutive relations for solids: An internal-variable theory and its application to metal plasticity. *J. Mech. Phys. Solids*, 19, (1971), 433 – 455.
- Rosochowski, A.; Olejnik, L.: Numerical and physical modelling of plastic deformation in 2-turn equal channel angular extrusion. *Journal of Materials Processing Technology*, 125126, 0, (2002), 309 – 316.
- Rosochowski, A.; Olejnik, L.: Finite element analysis of two-turn incremental ecap. *International Journal of Material Forming*, 1, 1, (2008), 483–486.
- Segal, V.: Materials processing by simple shear. *Materials Science and Engineering: A*, 197, 2, (1995), 157 – 164.
- Segal, V.: Equal channel angular extrusion: from macromechanics to structure formation. *Materials Science and Engineering: A*, 271, 12, (1999), 322 – 333.
- Segal, V.; Reznikov, V.; Drobyshevskii, A.; Kopylov, V.: Plastic treatment of metals by simple shear. *Izv. Akad. Nauk SSSR, Ser. Met.*, 1, (1981), 115–123.
- Srinivasa, A.; Srinivasan, S.: *Inelasticity of Single Crystals*, chap. 13, pages 455–494. World Scientific (2009).